

REPORT DOCUMENTATION PAGEForm Approved
OMB NO. 0704-0188

Public Reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comment regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave Blank)		2. REPORT DATE February 12, 2004	3. REPORT TYPE AND DATES COVERED Final Progress Report - 5/15/00 - 11/14/03
4. TITLE AND SUBTITLE Fundamental Investigation on Processing of High Performance Covalent Ceramic Nanocomposite by Polymer Precursor Pyrolysis		5. FUNDING NUMBERS DAAD-19-00-1-0185	
6. AUTHOR(S) Joshua Kuntz, Guo-Dong Zhan, Amiya Mukherjee			
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) University of California One Shields Avenue, Davis, CA 95616		8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) U. S. Army Research Office P.O. Box 12211 Research Triangle Park, NC 27709-2211		10. SPONSORING / MONITORING AGENCY REPORT NUMBER 40013.19 - ms	
11. SUPPLEMENTARY NOTES The views, opinions and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy or decision, unless so designated by other documentation.			
12 a. DISTRIBUTION / AVAILABILITY STATEMENT Approved for public release; distribution unlimited.		12 b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) Alumina based ceramic nanocomposites were investigated with the objective of improving fracture toughness. Specific focus during processing was directed at the retention of nanocrystalline microstructures in the matrix of the composites while still achieving full density. Second phases were added to the alumina matrix to investigate the applicability of toughening mechanisms that have been developed earlier for microcrystalline ceramics. The use of spark plasma sintering technique allowed the retention of ultrafine grain size of alumina due to lowered sintering temperatures and shorter sintering times. Very attractive improvements in fracture toughness were noted in Al ₂ O ₃ /Nb, Al ₂ O ₃ /carbon nanotube, Al ₂ O ₃ /SiC whisker, and Al ₂ O ₃ /Nb/carbon nanotube composites. The results were analyzed in the context of effective toughening mechanisms in these nanocrystalline matrices.			
14. SUBJECT TERMS alumina, ceramic nanocomposites, processing & characterization, fracture toughness			15. NUMBER OF PAGES
			16. PRICE CODE
17. SECURITY CLASSIFICATION OR REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION ON THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL

NSN 7540-01-280-5500

Standard Form 298 (Rev.2-89)
Prescribed by ANSI Std. Z39-18
298-102

Enclosure 1

20040315 066

TABLE OF CONTENTS

Memorandum of Transmittal	i
Standard Form 298	ii
Report of Inventions & Subcontracts (DD Form 882).....	iii
Table of Contents	1
Foreword	2
Statement of Problem Studied	3
Summary of Results	4
Publications Published in Peer-Review Journals.....	7
Papers Published in Non-Peer Reviewed Journals or Conference Proceedings	7
Papers Presented at Meetings, But Not Published in Conference Proceedings	8
Manuscripts Submitted, But Not Published.....	9
Technical Reports Submitted to ARO	9
List of Participating Scientific Personnel.....	11
Report of Inventions.....	11
Bibliography	12

**FUNDAMENTAL INVESTIGATION ON PROCESSING OF
HIGH PERFORMANCE COVALENT CERAMIC NANOCOMPOSITES
BY POLYMER PRECURSOR PYROLYSIS**

FINAL PROGRESS REPORT

ARO GRANT #DAAD19-00-1-0185

FOREWORD:

This is the Final Progress Report of the ARO Grant on improving the mechanical properties of ceramic nanocomposites. Ceramics have many attractive attributes, e.g., chemical inertness, abrasion, and erosion resistance, high temperature strength, etc. However, they all, in general, lack adequate values of fracture toughness.

In this investigation, we have succeeded in raising the fracture toughness of single-phase alumina by almost four or five times by taking advantage of ductile-phase toughening, fiber-toughening, transformation-toughening, and a combination of ductile-phase and fiber-toughening.

The results have been published in several peer-reviewed archival journals and have been presented in national and international conferences. The University of California has also filed five patent applications in the related subject areas.

DISTRIBUTION STATEMENT A

Approved for Public Release
Distribution Unlimited

STATEMENT OF THE PROBLEM STUDIED:

The goal of this project was to gain a fundamental understanding of the processing and properties of ceramic nanocomposites. Specific focus during processing was directed at the retention of nanocrystalline microstructures in the matrix of the composites while still achieving full density. Alumina was chosen as the base matrix material to obtain general understandings that might also be applicable to other ceramic systems. Second phases have been added to the nanocrystalline alumina matrix to investigate the applicability of toughening mechanisms that have been thoroughly developed in microcrystalline ceramics. The mechanisms of interest were ductile-phase toughening, fiber toughening, and transformation toughening.

One of the drawbacks of toughening conventional ceramics is the decrease in strength and hardness that typically accompany the introduction of second phases into the base material. Nanocrystalline matrix ceramic composites can overcome this obstacle through the balancing of the softening/weakening effect of the second phases through the increases in hardness and strength that accompany refinement of grain size into the nanoscale.

The materials systems investigated were as follows:

Ductile-phase toughening:

-- Alumina-Niobium

Fiber toughening:

-- Alumina-Silicon Carbide Whiskers

-- Alumina-Carbon Nanotubes

Transformation toughening:

-- Alumina-Zirconia

-- Alumina-Barium Titanate

-- Alumina-Neodymium Titanate

SUMMARY OF RESULTS:

MATERIAL PREPARATION & CONSOLIDATION

High-Energy Ball-Milling:

Mechanical attrition (high-energy ball-milling, HEBM) as a refinement technique has been widely used for preparation of nanocrystalline metallic materials. This method has now been applied to preparation of ceramic nanopowders. HEBM is known to be able to bring about a number of effects on oxides, which greatly enhances solid-state phase transformation. The effect of milling on the phase transformation and microstructural development can be postulated as follows. First, HEBM can lead to higher green density of the compacts due to pore collapse from the high compressive and shear stresses during the milling. Second, the high energetic level and highly localized internal energy distribution of the HEBM powder might provide additional nucleation energy to overcome the phase transformation barrier. The residual stress induced by HEBM is likely responsible for this broadening of the XRD peaks seen in Figure 1. All these effects along with the effect from electric-field-assisted-sintering, lead to the optimized condition for forming of nanocrystalline alumina nanocomposites.

Typical powder processing for the composites in this study included the as-received γ - Al_2O_3 nanopowder being first mechanically milled using HEBM (in a Spex 8000 mixer mill in a WC ball and vial) with one weight percent polyvinyl alcohol (PVA), a dry milling agent, to prevent severe powder agglomeration. Milling was followed by a vacuum heat treatment at 350°C for 3 hrs, for the removal of the PVA.

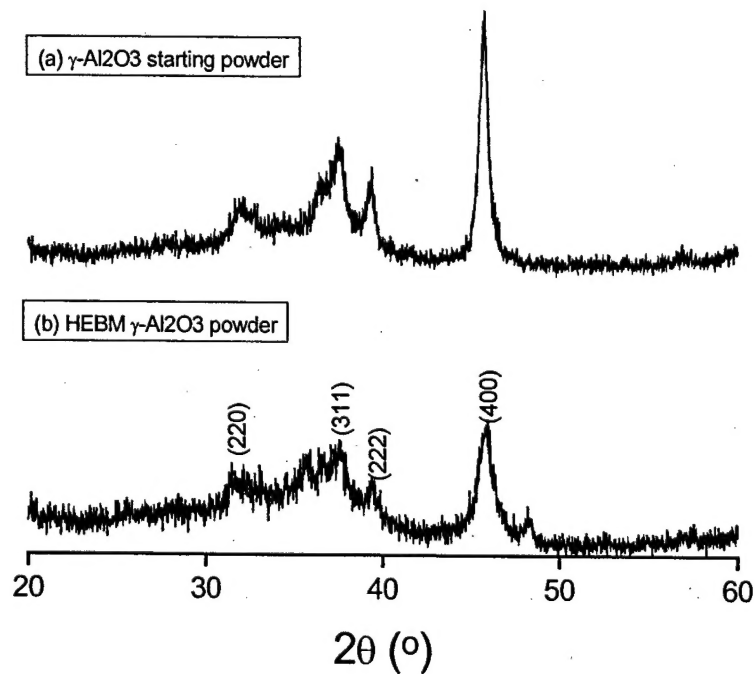


Figure 1. XRD profiles for (a) as-received γ - Al_2O_3 and (b) HEBM γ - Al_2O_3 nanopowders.

Spark Plasma Sintering:

One of the main difficulties to the sintering of nanocrystalline ceramics is the ability to retain a nano-scale grain size and still obtain full density. The advanced consolidation technique employed in the present study to overcome this hurdle is spark plasma sintering, SPS. It is a pressure-assisted sintering method based on the supposition of the presence of high temperature plasma (spark plasma) momentarily generated in the gaps between powder particles by electrical discharge during DC pulsing. SPS can rapidly consolidate powders to near theoretical density through the combined effects of rapid heating rate, pressure application, and electrical pulsing. In the present study, powder consolidation was carried out under vacuum in a Dr. Sinter 1050 SPS apparatus. The processing parameters used in the present study were as follows: an applied pressure of 80 MPa, an "On" pulse of 12 cycles of 2 ms each and the "Off" interval between pulses of 2 cycles, and maximum pulse parameters of 5000 A and 10 V. After applying the given pressure, samples were heated to 600 °C in 2 minutes and then ramped to their sintering temperature using heating rates ranging from 150 °C/min to 500 °C/min.

MATERIAL Parameters and the Resultant Properties

- Al_2O_3 -10 vol.% Nb ductile phase toughened compositeⁱ:
 - ⇒ Using consolidation parameters of only 3 minutes and 1100 °C by SPS this material has been consolidated to full density.
 - ⇒ The alumina matrix grain size is ~200 nm and the niobium grain size is ~20 nm.
 - ⇒ This composite has a hardness of 22.5 GPa (slightly higher than pure alumina) and a fracture toughness of 7.0 MPam^{1/2} (more than twice that of pure alumina).
- Al_2O_3 -20 vol.% SiC_w fiber toughened compositeⁱⁱ:
 - ⇒ The consolidation of this composite dramatically demonstrates the effect of HEBM on sintering kinetics. In only 3 minutes at 1150 °C by SPS, HEBM powders were consolidated to 100% TD. Non-HEBM powders achieved only 80% TD under the same sintering conditions (100% TD required 1250 °C).
 - ⇒ The HEBM specimen also retained a finer alumina grain size, 146 nm.
 - ⇒ The resulting mechanical properties were a hardness of 26.4 GPa and a fracture toughness of 6.0 MPam^{1/2}.
- Al_2O_3 -10 vol.% SWCN fiber toughened composite:
 - ⇒ The alumina-single walled carbon nanotube (SWCN) composite was consolidated to full density by wet ball-milling followed by SPS at 1150 °C for 3 minutes.

- ⇒ This material retained a hardness of 16.1 GPa while demonstrating a fracture toughness of $9.7 \text{ MPam}^{1/2}$.
- ⇒ Due to the electrically conducting nature of the SWCN the composite is 13 orders of magnitude more conductive than pure alumina, 1510 S/m.
- Al_2O_3 -20 vol.% 3Y-TZP transformation toughened compositeⁱⁱⁱ:
 - ⇒ The HEBM powders for this composite were successfully consolidated to full density by SPS at 1100 °C for 3 minutes.
 - ⇒ Grain growth in this composite was limited to such an extent that the consolidated grain size was only 96 nm.
 - ⇒ This material also exhibited a remarkable fracture toughness of $8.9 \text{ MPam}^{1/2}$.
- Al_2O_3 -5 vol.% Nb-5 vol.% SWCN synergistically toughened composite:
 - ⇒ Using consolidation parameters of only 3 minutes and 1150 °C by SPS this material has been consolidated to full density.
 - ⇒ This material retained a hardness of 13.8 GPa while demonstrating a fracture toughness of $14.2 \text{ MPam}^{1/2}$.

PUBLICATIONS PUBLISHED IN PEER-REVIEWED JOURNALS:

J. D. Kuntz, G.-D. Zhan, and A. K. Mukherjee, "Nanocrystalline Matrix Ceramic Composites for Improved Fracture Toughness," MRS Bulletin, (in press, Jan. 2004).

G.-D. Zhan, J. D. Kuntz, J. E. Garay, and A. K. Mukherjee, "Electrical Properties of Nanoceramics Reinforced with Ropes of Single-Walled Carbon Nanotubes," Applied Physics Letters, 83, 1228-1230, (2003).

G.-D. Zhan, J. D. Kuntz, J. Wan, and A. K. Mukherjee, "Single-Wall Carbon Nanotubes as Attractive Toughening Agents in Alumina-Based Nanocomposites," Nature Materials, 2, 38-42, (2003)

G.-D. Zhan, J. D. Kuntz, J. Wan, J. E. Garay, and A. K. Mukherjee, "A Novel Processing Route to Develop a Dense Nanocrystalline Alumina Matrix (<100nm) Nanocomposite Material," Journal of the American Ceramic Society, 86 [1]200-202, (2003).

G.-D. Zhan, J. D. Kuntz, J. Wan, J. E. Garay, and A. K. Mukherjee, "Single-Wall Carbon Nanotubes Reinforced Alumina Nanocomposites Consolidated by Spark-Plasma-Sintering," Ceramic Nanomaterials and Nanotechnology, pp. 161-169, (2003).

G.-D. Zhan, J. D. Kuntz, J. Wan, J. E. Garay, and A. K. Mukherjee, "Spark-Plasma-Sintered BaTiO₃/Al₂O₃ Nanocomposites," Materials Science & Engineering A, A356, 443-446, (2003).

G.-D. Zhan, J. D. Kuntz, J. Wan, J. E. Garay, and A. K. Mukherjee, "Alumina-based Nanocomposites Consolidated by Spark Plasma Sintering," Scripta Materials, 47, 737-741, (2002).

PAPERS PUBLISHED IN NON-PEER REVIEWED JOURNALS OR IN CONFERENCE PROCEEDINGS:

G.-D. Zhan, J. D. Kuntz, J. Wan, and A. K. Mukherjee, "Plasticity in Nanomaterials," 2002 MRS Fall Meeting Proceedings, Boston, MA, pp. 41-48, (2003).

J. D. Kuntz, G.-D. Zhan, and A. K. Mukherjee, "Properties and Microstructure of Alumina-Niobium and Alumina-Neodymium Titanate Nanocomposites Made by Novel Processing Methods," Proceedings of 26th Annual Int'l Conference & Exposition on Advanced Ceramics and Composites, (2002).

J. D. Kuntz, J. Wan, G.-D. Zhan, and A. K. Mukherjee, "Properties and Microstructure of Alumina-Niobium Nanocomposites Made by Novel Processing Methods," *Ultrafine Grained Materials II*, pp. 225-233, Ed. by Y.T. Zhu, T.G. Langdon, R.S. Mishra, S.L. Semiatin, M.J. Saran, and T.C. Lowe, (2002).

G.-D. Zhan, J. D. Kuntz, J. Wan, J. E. Garay, and A. K. Mukherjee, "Synthesis of $\text{Nd}_2\text{Ti}_2\text{O}_7/\text{Al}_2\text{O}_3$ Nanocomposites by Spark-Plasma-Sintering and High-Energy Ball-Milling," *Ultrafine Grained Materials II*, pp. 219-224, Ed. by Y.T. Zhu, T.G. Langdon, R.S. Mishra, S.L. Semiatin, M.J. Saran, and T.C. Lowe, (2002).

J. Wan, M. J. Gasch, J. D. Kuntz, R. S. Mishra, and A. K. Mukherjee, "Processing and Properties of Ceramic Nanocomposites Produced from Polymer Precursor Pyrolysis, High Pressure Sintering, and Spark Plasma Sintering," *Materials Research Society Symposium Proceedings*, 634, B7.2.1-B7.2.6, (2001).

PAPERS PRESENTED AT MEETINGS, BUT NOT PUBLISHED IN CONFERENCE PROCEEDINGS:

Joshua D. Kuntz, Ren-Guan Duan, Guo-Dong Zhan, & Amiya K. Mukherjee. "High-Strain-Rate Superplasticity and Formability Studies in $\text{Al}_2\text{O}_3\text{-ZrO}_2\text{-MgAl}_2\text{O}_4$ Nanocomposites." Presented at 55th Pacific Coast Regional & Basic Science Division Fall Meeting - ACERS 2003.

Guo-Dong Zhan, Joshua D. Kuntz, Hsin Wang, Chongmin Wang, Javier Garay, Ren-Guan Duan, & Amiya K. Mukherjee. "Multifunctional Carbon Nanotube/Ceramic Nanocomposites Produced by Spark-Plasma-Sintering." Presented at 55th Pacific Coast Regional & Basic Science Division Fall Meeting - ACERS 2003.

Guo-Dong Zhan, Joshua D. Kuntz, Hsin Wang, Chongmin Wang, Javier Garay, Ren-Guan Duan, & Amiya K. Mukherjee. "Single-Wall Carbon Nanotube Reinforced Nanoceramics with Novel Electrical and Thermal Properties." Presented at 55th Pacific Coast Regional & Basic Science Division Fall Meeting - ACERS 2003.

Joshua D. Kuntz, Guo-Dong Zhan, & Amiya K. Mukherjee. "Synthesis and Processing of Single-wall Carbon Nanotubes/Ceramic Nanocomposites with Novel Properties." Presented at the Materials Research Society Spring Meeting 2003.

Guo-Dong Zhan, Michael J. Reece, Joshua D. Kuntz, & Amiya K. Mukherjee. "Piezoelectric Neodymium Titanate Nanoceramics Produced by Novel Spark-Plasma-Sintering Technique." Presented at the Materials Research Society Spring Meeting 2003.

Guo-Dong Zhan, Joshua D. Kuntz, Rong-Jun Xie, & Amiya K. Mukherjee.
"Processing of Barium Titanate Nanoceramics with Novel Dielectric Properties."
Presented at the Materials Research Society Spring Meeting 2003.

Joshua D. Kuntz, Guo-Dong Zhan, Julin Wan, & Amiya K. Mukherjee. "Carbon Nanotube Reinforced Alumina Nanocomposites: Processing and Properties."
Presented at 54th Pacific Coast Regional & Basic Science Division Meeting - ACERS 2002.

Joshua D. Kuntz, Julin Wan, & Amiya K. Mukherjee. "High-Strain-Rate Superplasticity in $\text{Al}_2\text{O}_3/\text{ZrO}_2/\text{MgAl}_2\text{O}_4$ Nanocomposites." Presented at 54th Pacific Coast Regional & Basic Science Division Meeting - ACERS 2002.

Guo-Dong Zhan, Joshua D. Kuntz, Julin Wan, & Amiya K. Mukherjee.
"Synthesis of Alumina Based Nanocomposites for Improved Toughness."
Presented at 104th Annual Meeting & Exposition - ACERS 2002.

Guo-Dong Zhan, Joshua D. Kuntz, Julin Wan, Javier Garay, & Amiya K. Mukherjee. "Syntheses of $\text{Nd}_2\text{Ti}_2\text{O}_7/\text{Al}_2\text{O}_3$ Nanocomposites by Spark-Plasma-Sintering and High-Energy Ball-Milling." Presented at TMS Annual Meeting - 2002.

MANUSCRIPTS SUBMITTED, BUT NOT PUBLISHED:

Guo-Dong Zhan, Joshua Kuntz, Ren-Guan Duan, & Amiya Mukherjee,
"Processing Silicon Carbide Whiskers Reinforced Nanocrystalline Alumina Matrix Nanocomposites by Novel Processing Methods," submitted to Journal of the American Ceramic Society.

Guo-Dong Zhan, Joshua Kuntz, Hsin Wang, Chong-Min Wang, & Amiya Mukherjee, "Anisotropic Thermal Properties of Single-Wall Carbon Nanotube Reinforced Nanoceramics," submitted to Applied Physics Letters.

Guo-Dong Zhan & Amiya Mukherjee, "Carbon Nanotubes Reinforced Alumina-based Ceramics with Novel Mechanical, Electrical, and Thermal Properties," submitted to Applied Ceramic Technology.

TECHNICAL REPORTS SUBMITTED TO ARO:

Interim Report

Joshua D. Kuntz, Guodong Zhan, and Amiya K. Mukherjee
Fundamental Investigation on Processing of High Performance Covalent Ceramic Nanocomposites by Polymer Precursor Pyrolysis
03-30-2001

Interim Report

Joshua D. Kuntz, Guo-Dong Zhan, and Amiya K. Mukherjee

**Fundamental Investigation on Processing of High Performance Covalent Ceramic
Nanocomposites**

03-31-2002

Interim Report

Joshua D. Kuntz, Guo-Dong Zhan, and Amiya K. Mukherjee

**Fundamental Investigation on Processing of High Performance Covalent Ceramic
Nanocomposites by Polymer Precursor Pyrolysis**

05-05-2003

LIST OF ALL PARTICIPATING SCIENTIFIC PERSONNEL:

Principal Investigator:

Professor Amiya K. Mukherjee

Post-doctoral Researcher:

Dr. Guo-Dong Zhan

Graduate Student Researcher:

Joshua D. Kuntz

REPORT OF INVENTIONS:

G.-D. Zhan, J. D. Kuntz, and A. K. Mukherjee, Anisotropic Thermal Applications of Composites of Ceramics and Carbon Nanotubes, US patent pending, UC Case No. 2003-465-1 (Attorney Docket No.: 02307Z-137500US, Filed Jun. 26, 2003).

G.-D. Zhan, A. K. Mukherjee, J. D. Kuntz, and J. Wan, Processing of Nanocrystalline Barium Titanate Dielectric Material, US patent pending, UC Case No. 2003-010-1 (Attorney Docket No.: 02307Z-133000US, Filed Apr. 11, 2003).

J. D. Kuntz, G.-D. Zhan, and A. K. Mukherjee, Nanocrystalline Ceramic Materials Reinforced with Metal and Single-Wall Carbon Nanotubes, US patent pending, UC Case No. 2003-298-1 (Attorney Docket No.: 02370Z-133400US, Filed Feb. 26, 2003).

G.-D. Zhan, A. K. Mukherjee, J. D. Kuntz, and J. Wan, Nanocrystalline Ceramic Materials Reinforced with Single-Wall Carbon Nanotubes, US patent pending, UC Case No. 2003-028-1 (Attorney Docket No.: 02307Z-133100US, Filed Jan. 30, 2003).

G.-D. Zhan, J. D. Kuntz, and A. K. Mukherjee, Ceramic Materials Reinforced with Single-Wall Carbon Nanotubes as Electrical Conductors, US patent pending, UC Case No. 2003-299-1 (Attorney Docket No.: 02307Z-133500US, Filed Feb. 26, 2003).

G.-D. Zhan, J. D. Kuntz, J. Wan, and A. K. Mukherjee, Silicon Carbide Whisker-Reinforced Ceramics with Low Rate of Grain Size Increase Upon Densification, US patent pending, UC Case No. 2003-008-1 (Attorney Docket No.: 02307Z-129600US, Filed Dec. 18, 2003).

BIBLIOGRAPHY

ⁱ J. Kuntz, J. Wan, G.-D. Zhan, and A. K. Mukherjee (2002), "Properties and Microstructure of Alumina-Niobium Nanocomposites Made by Novel Processing Methods," *Ultrafine Grained Materials II*, ed. Y.T. Zhu, et al., TMS, 225-233 (2002).

ⁱⁱ G.-D. Zhan, J. Kuntz, J. Wan, and A. K. Mukherjee, "Development of Nanocrystalline Alumina Matrix Nanocomposites Toughened by Silicon Carbide Whiskers," *Journal of Materials Research*, (Submitted) 2002.

ⁱⁱⁱ G.-D. Zhan, J. Kuntz, J. Wan, J. Garay, and A. K. Mukherjee, "A Novel Processing Route to Develop a Dense Nanocrystalline Alumina Matrix (< 100 nm) Nanocomposite Material," *Journal of the American Ceramic Society*, (in review) 2002.